

See discussions, stats, and author profiles for this publication at: <https://www.researchgate.net/publication/240734375>

Lueshite, pyrochlore and monazite-(Ce) from apatite-dolomite carbonatite, Lesnaya Varaka complex, Kola Peninsula, Russia

Article in *Mineralogical Magazine* · December 1998

DOI: 10.1180/002646198548151

CITATIONS

67

READS

300

2 authors:



Anton Chakhmouradian

University of Manitoba

143 PUBLICATIONS 3,240 CITATIONS

[SEE PROFILE](#)



Roger H. Mitchell

Lakehead University Thunder Bay Campus

325 PUBLICATIONS 9,283 CITATIONS

[SEE PROFILE](#)

Some of the authors of this publication are also working on these related projects:



Perovskite-group minerals [View project](#)



Igneous carbonates [View project](#)

Lueshite, pyrochlore and monazite-(Ce) from apatite-dolomite carbonatite, Lesnaya Varaka complex, Kola Peninsula, Russia

A. R. CHAKHMOURADIAN AND R. H. MITCHELL

Department of Geology, Lakehead University, 955 Oliver Road, Thunder Bay, Ontario, Canada P7B 5E1

ABSTRACT

Apatite-dolomite carbonatite at Lesnaya Varaka, Kola Peninsula, Russia, hosts intricate mineral intergrowths composed of lueshite in the core and pyrochlore-group minerals in the rim. Lueshite is a primary Nb-bearing phase in the carbonatite and ranges in composition from cerian lueshite to almost pure NaNbO_3 . For comparison, the compositional variation of lueshite from the Kovdor and Sallanlatvi carbonatites is described. At Lesnaya Varaka, lueshite is replaced by nearly stoichiometric Na-Ca pyrochlore due to late-stage re-equilibration in the carbonatite system. X-ray powder diffraction data for both minerals are presented. Barian strontio-pyrochlore, occurring as replacement mantles on Na-Ca pyrochlore, contains up to 43% Sr and 8–18% Ba at the *A*-site, and shows a high degree of hydration and strong ionic deficiency at the *A*- and *Y*-sites. This mineral is metamict and, upon heating, recrystallises to an aeschynite-type structure. Monazite-(Ce) found as minute crystals in fractures, represents the solid solution between monazite-(Ce) CePO_4 , brabantite $\text{CaTh}(\text{PO}_4)_2$ and $\text{SrTh}(\text{PO}_4)_2$. Our data indicate the high capacity of the monazite structure for Th and accompanying divalent cations at low temperatures and pressures that has a direct relevance to solving the problem of long-term conservation of radioactive wastes. Monazite-(Ce) and barian strontio-pyrochlore are products of low-temperature hydrothermal or secondary (hypergene) alteration of the primary mineral assemblage of the carbonatite.

KEYWORDS: lueshite, pyrochlore, strontio-pyrochlore, monazite-(Ce), apatite-dolomite carbonatite, Lesnaya Varaka complex, Kola Peninsula.

Introduction

APATITE-dolomite carbonatite at Lesnaya Varaka hosts a number of niobium minerals, including natroniobite, for which it is a type locality (Bulakh *et al.*, 1960; Kukhareno *et al.*, 1965). The present work was undertaken to re-examine relationships between niobium-bearing accessory phases in apatite-dolomite carbonatite, and determine the compositional variation of most of these minerals for the first time. Given that there is some confusion regarding the definition of natroniobite in the literature, we also wished to re-investigate this mineral. Unfortunately, we were unable to locate the holotype specimen of natroniobite discovered by A.A. Kukhareno (Bulakh *et al.*, 1960). Hence we investigated

material from the Mineralogical Museum of St. Petersburg State University, Russia, labelled as 'natroniobite' in the Museum archives.

In addition to Lesnaya Varaka, natroniobite has also been described from the Sallanlatvi carbonatite, Kola Peninsula (Kukhareno *et al.*, 1965), the Elet'ozero alkaline intrusion, Karelia (Kukhareno *et al.*, 1969), and a vermiculite rock at the Gem Park Complex, Colorado (Parker and Sharp, 1970). In all these occurrences, natroniobite is an alteration product of primary Nb-rich minerals, mainly lueshite or pyrochlore. In most non-Russian mineralogical glossaries and reference-books, natroniobite is considered as a monoclinic polymorph of NaNbO_3 , dimorphous with orthorhombic lueshite (Safiannikoff, 1959) and cubic isolueshite (Chakhmouradian *et al.*,

1997); both of which belong to the perovskite mineral group. However, the original structural formula of natroniobite, given as $\text{NaNb}_2\text{O}_5(\text{OH})$ (Kukhareno *et al.*, 1965), rules out any links to the perovskite group, and suggests a relationship to AB_2O_6 -type oxides. XRD studies of natroniobite suggest that this mineral represents a Na-analogue of either fersmite (Kukhareno *et al.*, 1965) or aeschynite (Gorzhevskaya *et al.*, 1974).

Lueshite is a common accessory phase in the carbonatite occurrences at the Kola Peninsula, including Lesnaya Varaka (Kirillov and Burova, 1967; Orlova *et al.*, 1963; Rimskaia-Korsakova *et al.*, 1963), and elsewhere (Bagdasarov *et al.*, 1962; Parker and Sharp, 1970; Safiannikoff, 1959). However, only a few microprobe analyses are available for lueshite from the Sebljavr complex, Kola Peninsula (Subbotin and Men'shikov, 1987) and Lueshe, Zaire (Mitchell, 1996). Most other descriptions either lack compositional data or include bulk, mostly wet-chemical, analyses. This is reflected in the poor recalculation of the analyses into structural formulae and unrealistically high contents of such components as Al_2O_3 , SiO_2 and MgO . During this study, lueshite was identified as one of the major Nb-bearing accessories in the Lesnaya Varaka carbonatite. Accordingly, we have concentrated on the compositional variation of this mineral and also examined samples of lueshite from other carbonatite occurrences, including the Kovdor and Sallanlatvi complexes, Kola Peninsula.

Occurrence and phase relationships

The Lesnaya Varaka complex was intensively studied in the 1950s and 1960s by a group of scientists, headed by A.A. Kukhareno, from the Russian Geological Institute (St. Petersburg) and St. Petersburg State University. The geology, petrology and mineralogy of this, and other Middle-Palaeozoic carbonatite complexes of the Kola Peninsula, were described by Kukhareno *et al.* (1965). During the following three decades, olivinites from the Lesnaya Varaka pluton were investigated as a possible source of refractory raw material and platinum-group metals. The mineralogy of carbonatites and other minor lithologies exposed at Lesnaya Varaka has, as yet, not been examined in detail.

The complex is situated in the western part of Kola Peninsula, Russia ($67^\circ 23' \text{ N}$, $33^\circ 04' \text{ E}$), in the vicinity of Khabozero village. The complex is

expressed topographically as a ridge surrounded by lowlands, and from the east and north-east, by the Segozero Lake. The ridge is forested and exposures are typically lacking, except for a few prospecting trenches and pits in the central and eastern parts of the pluton. The geological description given below is according to Kukhareno *et al.* (1965).

The intrusion covers an area of about 9 sq. km, and is composed predominantly of olivinites, including varieties enriched in titaniferrous magnetite and perovskite. At the southern contact, the olivinites grade into clinopyroxenite through a modally transitional olivine-clinopyroxene rock. In the central part of the complex, the olivinites are cut by dikes of alkaline rocks (foirolites and phonolites) and dolomite carbonatites, including 'pure' dolomite and apatite-dolomite varieties. Nb-REE mineralization is confined to the latter. The apatite-dolomite carbonatite occurs as veins rimmed at their selvages by tremolite-dolomite aggregate. The rock commonly shows flow texture due to the alignment of apatite prisms along contacts.

Apatite-dolomite carbonatite examined in this study is fresh, yellowish-white in colour, fine-grained and composed mainly of dolomite (80–85 vol.%) and fluorapatite (less than 20 vol.%). Dolomite is close to its ideal composition and contains 4–8 mol.% ankerite. Fluorapatite is enriched in SrO and LREE_2O_3 (up to 12.8 and 1.8 wt.%, respectively). Accessory phases include biotite, strontianite and complex intergrowths of minerals. The latter are referred to as natroniobite in the Museum archives, and are composed of a black core and a thick (1–2.5 mm) honey-yellow replacement rim. In thin sections, the core is pinkish-brown, birefringent and shows polysynthetic twinning typical of low-symmetry members of the perovskite group. The replacement rim is pale yellow, optically isotropic or turbid, and shows no pleochroism. Back-scattered electron (BSE) imagery, compositional data and X-ray powder diffractometry (see below), show that the intergrowths are composed of lueshite in the core and pyrochlore-group minerals in the rim (Fig. 1). Lueshite commonly encloses irregular dolomite inclusions containing minute crystals of fluorapatite, anatase and ilmenite. The latter two minerals were not observed in the dolomite matrix outside of the lueshite crystals. Late fractures in both core and rim of the intergrowths host irregular grains of monazite-(Ce) up to 20 μm in size.

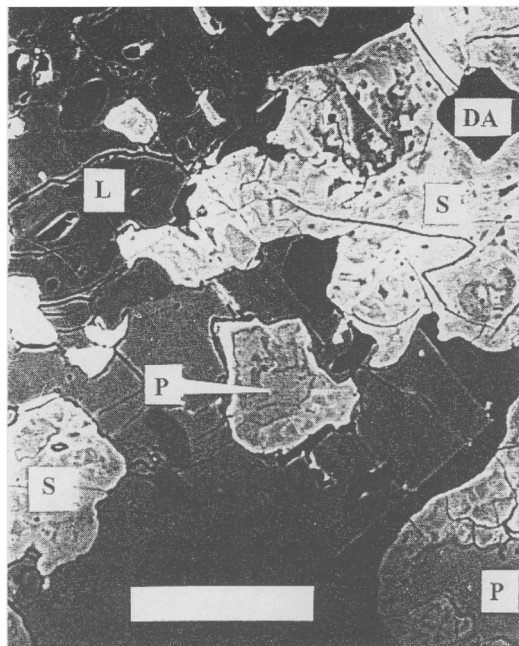


FIG. 1. BSE image of the lueshite-pyrochlore aggregate from apatite-dolomite carbonatite of the Lesnaya Varaka complex. L - lueshite, P - Na-Ca pyrochlore, S - barium strontio-pyrochlore, DA - dolomite + fluorapatite. Scale bar is 50 μm .

Mineral chemistry

Compositions of the minerals described in the present work were determined by X-ray energy-dispersive spectrometry (EDS) using a Hitachi 570 scanning electron microscope equipped with a LINK ISIS analytical system incorporating a Super ATW Light Element Detector, located at Lakehead University, Ontario. EDS spectra were acquired at an accelerating voltage of 20 kV and beam current of 0.86 nA. The following well-characterized natural and synthetic standards were employed for the determination of mineral compositions: Khibina loparite (*LREE*), Lueshite lueshite (Na, Nb), Magnet Cove perovskite (Ca, Ti, Fe), apatite (P), jeppite (Ba), synthetic SrTiO_3 (Sr), metallic Ta and Th. The accuracy of the method was cross-checked by wave-length-dispersive electron microprobe analysis using an automated CAMECA SX-50 microprobe located at the University of Manitoba, following techniques described by Mitchell and Vladykin (1993).

Lueshite

BSE imagery reveals complex zonation of the lueshite crystals. The crystals typically exhibit irregular *LREE*-enriched cores and Ca- and Ti-enriched rims (Fig. 1). A series of thin irregular zones between the core and rim, which cover the core-to-rim compositional range, are collectively described here as an intermediate zone. The irregular outline of separate zones, presumably indicates repeated dissolution and growth of the crystals. Crystals of lueshite from Kovdor (dolomite carbonatite) and Sallanlatvi (calcite carbonatite) also show irregular zonation reflecting a very complex crystallization history of the mineral. Representative compositions of lueshite from Lesnaya Varaka and these other localities are given in Table 1. Data were recalculated into perovskite-type end-members following the methods described by Mitchell (1996). Most of the compositions can be adequately characterized using only three end-member components: lueshite NaNbO_3 , loparite-(Ce) $\text{NaCeTi}_2\text{O}_6$ and perovskite CaTiO_3 (Fig. 2). The contents of SrTiO_3 , CaThO_3 and other end-members are negligible (Table 1). As demonstrated in Fig. 2, lueshite from Lesnaya Varaka compositionally evolves from cerian lueshite to lueshite *sensu stricto*. Samples of lueshite from the Kovdor and Sallanlatvi carbonatites differ significantly from Lesnaya Varaka lueshite in their compositional ranges and evolutionary trends. Our data (Table 1) and those available from the literature (Bagdasarov *et al.*, 1962; Subbotin and Men'shikov, 1987) demonstrate that lueshite from dolomite carbonatites is generally richer in LREE_2O_3 , compared with that from calcite carbonatites. Among the latter, the highest LREE_2O_3 content was reported in lueshite from Sebljavr (2.6 wt.%: Subbotin and Men'shikov, 1987).

Pyrochlore

Pyrochlore developed on lueshite shows a wide compositional range from 'normal' almost stoichiometric Na-Ca pyrochlore to Na-poor Sr- and Ba-rich pyrochlore. Using the pyrochlore-group nomenclature suggested by Hogarth (1989), the latter should be classified as barium strontio-pyrochlore ($\text{Sr} > 20\% \Sigma A\text{-cations}$; $\text{Ba} > 8\% \Sigma A\text{-cations}$).

Representative compositions of Na-Ca pyrochlore are given in Table 2. Structural formulae of this mineral, recalculated on the basis of two B-cations ($\text{Nb} + \text{Ti} + \text{Fe}^{3+}$), are close to the ideal

TABLE 1. Representative compositions of lueshite

| Wt. % | 1 | 2 | 3 | 4 | 5 | 6 | 7 | 8 | 9 | 10 | 11 |
|------------------------------------|-------|--------|--------|--------|-------|--------|-------|-------|--------|--------|-------|
| Na ₂ O | 15.27 | 16.42 | 16.53 | 16.27 | 15.62 | 15.78 | 15.49 | 15.49 | 15.69 | 14.91 | 15.63 |
| CaO | 1.19 | 1.42 | 2.04 | 2.04 | 2.93 | 0.86 | 2.63 | 2.27 | 1.80 | 3.07 | 1.79 |
| SrO | 0.47 | 0.35 | 0.52 | 0.23 | 0.24 | 0.45 | 0.46 | 0.44 | 0.25 | n.d. | n.d. |
| La ₂ O ₃ | 1.05 | 0.80 | n.d. | 0.04 | 0.24 | 1.15 | 0.42 | 0.97 | 0.33 | 0.06 | n.d. |
| Ce ₂ O ₃ | 2.70 | 1.99 | 1.20 | 1.53 | 1.34 | 2.48 | 0.96 | 2.76 | 0.63 | 0.43 | 0.33 |
| Pr ₂ O ₃ | n.d. | n.d. | n.d. | 0.14 | n.d. | n.d. | n.d. | n.d. | 0.31 | n.d. | n.d. |
| Nd ₂ O ₃ | 0.65 | 0.36 | 0.19 | 0.27 | 0.08 | 0.10 | 0.27 | 0.35 | n.d. | n.d. | 0.29 |
| ThO ₂ | 0.71 | 2.28 | 1.30 | 1.71 | 0.31 | 0.15 | 0.24 | n.d. | n.d. | 0.13 | n.d. |
| TiO ₂ | 3.41 | 5.18 | 3.78 | 5.61 | 5.39 | 2.98 | 5.97 | 5.36 | 3.61 | 4.24 | 3.16 |
| Fe ₂ O ₃ | 0.34 | 0.22 | 0.30 | 0.10 | n.d. | 0.10 | n.d. | 0.09 | 0.08 | 0.45 | 0.63 |
| Nb ₂ O ₅ | 73.96 | 71.24 | 74.33 | 72.20 | 72.41 | 76.00 | 71.82 | 70.95 | 78.07 | 74.68 | 76.52 |
| Ta ₂ O ₅ | n.d. | n.d. | n.d. | n.d. | n.d. | n.d. | n.d. | n.d. | n.d. | 2.15 | n.d. |
| Total | 99.75 | 100.26 | 100.19 | 100.14 | 98.56 | 100.05 | 98.26 | 98.68 | 100.77 | 100.12 | 98.35 |
| Structural formulae (O = 3) | | | | | | | | | | | |
| Na | 0.821 | 0.877 | 0.876 | 0.860 | 0.830 | 0.841 | 0.824 | 0.832 | 0.817 | 0.783 | 0.831 |
| Ca | 0.035 | 0.042 | 0.060 | 0.060 | 0.086 | 0.025 | 0.077 | 0.067 | 0.052 | 0.089 | 0.053 |
| Sr | 0.007 | 0.006 | 0.008 | 0.004 | 0.004 | 0.007 | 0.007 | 0.007 | 0.004 | 0.000 | 0.000 |
| La | 0.011 | 0.008 | 0.000 | 0.000 | 0.002 | 0.012 | 0.004 | 0.010 | 0.003 | 0.001 | 0.000 |
| Ce | 0.027 | 0.020 | 0.012 | 0.015 | 0.013 | 0.025 | 0.010 | 0.028 | 0.006 | 0.004 | 0.003 |
| Pr | 0.000 | 0.000 | 0.000 | 0.001 | 0.000 | 0.000 | 0.000 | 0.000 | 0.003 | 0.000 | 0.000 |
| Nd | 0.006 | 0.004 | 0.002 | 0.003 | 0.001 | 0.001 | 0.003 | 0.004 | 0.000 | 0.000 | 0.003 |
| Th | 0.004 | 0.014 | 0.008 | 0.011 | 0.002 | 0.001 | 0.002 | 0.000 | 0.000 | 0.001 | 0.000 |
| Ti | 0.071 | 0.107 | 0.078 | 0.115 | 0.111 | 0.062 | 0.077 | 0.067 | 0.073 | 0.086 | 0.065 |
| Fe | 0.007 | 0.004 | 0.006 | 0.002 | 0.000 | 0.002 | 0.000 | 0.002 | 0.002 | 0.009 | 0.013 |
| Nb | 0.927 | 0.887 | 0.918 | 0.890 | 0.898 | 0.945 | 0.891 | 0.889 | 0.948 | 0.914 | 0.949 |
| Ta | 0.000 | 0.000 | 0.000 | 0.000 | 0.000 | 0.000 | 0.000 | 0.000 | 0.000 | 0.016 | 0.000 |
| Mol. % end-members | | | | | | | | | | | |
| NaNbO ₃ | 85.46 | 88.39 | 90.01 | 89.12 | 86.85 | 88.18 | 87.28 | 83.42 | 90.89 | 88.73 | 92.71 |
| CaTiO ₃ | 3.40 | 2.89 | 5.39 | 5.19 | 8.98 | 2.68 | 8.19 | 7.11 | 5.85 | 10.07 | 5.91 |
| NaCeTi ₂ O ₆ | 9.82 | 6.64 | 2.90 | 4.18 | 3.56 | 8.25 | 3.58 | 8.73 | 2.82 | 1.11 | 1.38 |
| SrTiO ₃ | 0.83 | 0.58 | 0.86 | 0.39 | 0.41 | 0.79 | 0.79 | 0.75 | 0.44 | 0.00 | 0.00 |
| CaThO ₃ | 0.49 | 1.50 | 0.84 | 1.12 | 0.21 | 0.10 | 0.16 | 0.00 | 0.00 | 0.09 | 0.00 |

Compositions: 1 core, 2–3 intermediate zone and 4 rim of a zoned lueshite crystal, Lesnaya Varaka; 5 core, 6–7 intermediate zone and 8 rim of a zoned lueshite crystal, Kovdor; 9–11 core, intermediate zone and rim of a zoned lueshite crystal, Sallanlatvi. Total Fe expressed as Fe₂O₃; n.d = not detected.

formula NaCaNb₂O₆(F, OH). This pyrochlore contains moderate *LREE*₂O₃, SrO and TiO₂ and shows a low cation deficiency at the *A*-site (0.05–0.39 apfu). In places, Na-Ca pyrochlore is enriched in ThO₂ (up to 5.7–5.8 wt.%). The ThO₂ content correlates negatively with CaO (Fig. 3) and shows no correlation with other major and minor components. This suggests that Th is accommodated in this mineral according to the following isomorphic scheme:



Barian strontio-pyrochlore (Ba-strontio-pyrochlore hereafter) is developed in peripheral zones and along fractures within the primary 'normal' pyrochlore. This mineral exhibits strong compositional variation with respect to CaO, SrO, BaO and Nb₂O₅ (Table 3). Ba-strontio-pyrochlore compositionally evolves by becoming depleted in Ca and enriched in Sr plus Ba at essentially constant *LREE* and Th (Fig. 4A,C,D). The depletion in Na and Ca is accompanied by increasing cation deficiency at the *A*-site (Fig. 4B). Recalculation of the analyses of this mineral gives approximately 6 atoms of

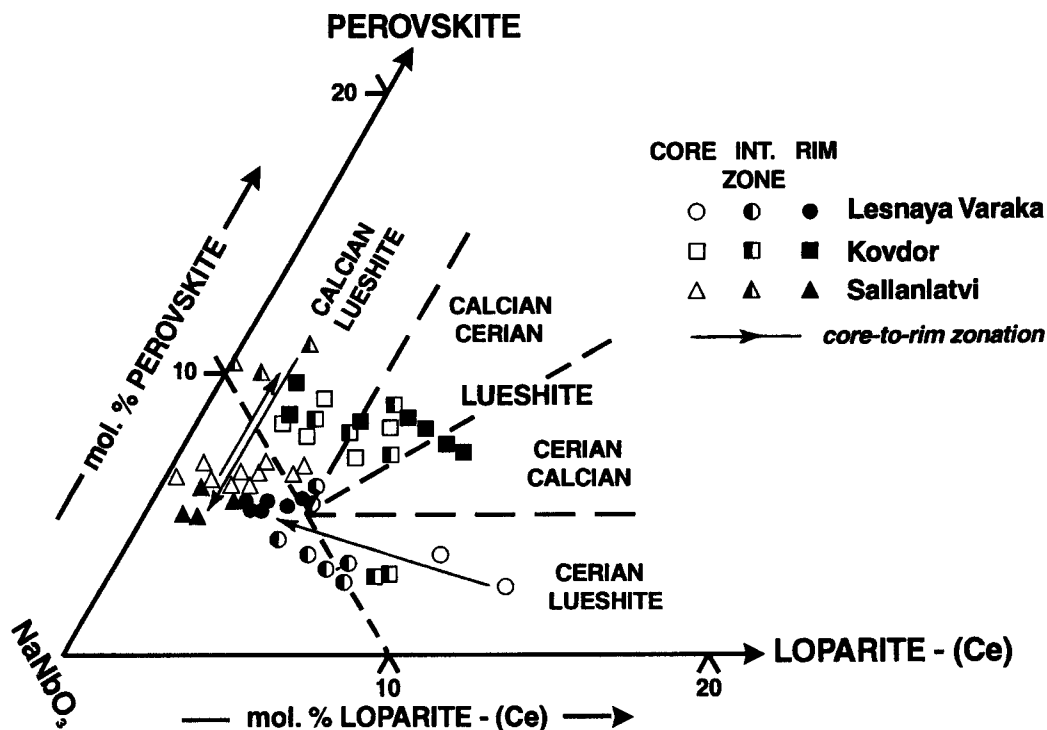


FIG. 2. Compositions (mol.%) of lueshite from the Lesnaya Varaka, Kovdor and Sallanlatvi carbonatites in the ternary system lueshite NaNbO_3 -perovskite CaTiO_3 -loparite-(Ce) $\text{NaCeTi}_2\text{O}_6$.

TABLE 2. Representative compositions of Na-Ca pyrochlore

| | 1 | 2 | 3 | 4 | 5 | | 1 | 2 | 3 | 4 | 5 |
|-------------------------|-------|-------|-------|-------|-------|--|-------|-------|-------|-------|-------|
| Wt. % | | | | | | Structural formulae ($\Sigma\text{B-cations} = 2$) | | | | | |
| Na_2O | 7.24 | 7.27 | 6.87 | 4.91 | 6.06 | Na | 0.864 | 0.877 | 0.844 | 0.590 | 0.735 |
| CaO | 13.68 | 12.77 | 12.57 | 12.16 | 11.27 | Ca | 0.902 | 0.851 | 0.853 | 0.808 | 0.756 |
| SrO | 1.15 | 1.14 | 1.07 | 1.06 | 0.81 | Sr | 0.041 | 0.041 | 0.039 | 0.038 | 0.029 |
| La_2O_3 | 0.11 | 0.42 | n.d. | 1.20 | 1.01 | La | 0.002 | 0.010 | 0.000 | 0.027 | 0.023 |
| Ce_2O_3 | 1.85 | 2.07 | 1.94 | 3.12 | 2.55 | Ce | 0.042 | 0.047 | 0.045 | 0.071 | 0.058 |
| Nd_2O_3 | 0.40 | 1.03 | 0.94 | 0.16 | 0.37 | Nd | 0.009 | 0.023 | 0.021 | 0.004 | 0.008 |
| ThO_2 | 2.43 | 3.42 | 3.88 | 4.86 | 5.69 | Th | 0.034 | 0.048 | 0.056 | 0.069 | 0.081 |
| | | | | | | ΣA | 1.894 | 1.897 | 1.858 | 1.607 | 1.690 |
| TiO_2 | 2.62 | 3.00 | 2.72 | 3.31 | 3.01 | Ti | 0.121 | 0.140 | 0.130 | 0.154 | 0.142 |
| Fe_2O_3 | 0.11 | 0.11 | 0.21 | 0.15 | 0.10 | Fe | 0.005 | 0.005 | 0.010 | 0.007 | 0.005 |
| Nb_2O_5 | 67.35 | 65.93 | 64.97 | 65.58 | 65.52 | Nb | 1.874 | 1.854 | 1.860 | 1.839 | 1.854 |
| Total | 96.94 | 97.16 | 95.17 | 96.51 | 96.39 | | | | | | |

Total Fe expressed as Fe_2O_3 ;

F was detected on EDS spectra, but not analysed.

n.d. = not detected.

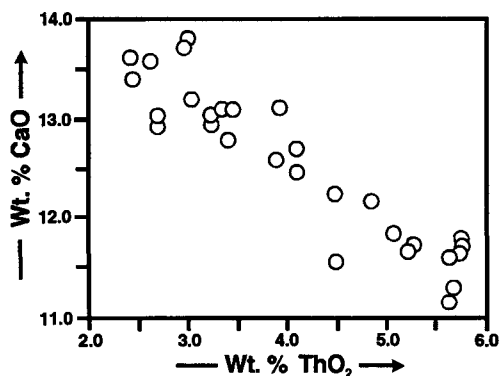


FIG. 3. Correlation between CaO and ThO₂ contents in Na-Ca pyrochlore, Lesnaya Varaka.

oxygen per 2 *B*-cations, indicating strong anion deficiency at the *Y*-site. Most compositions approach the generalized formula (Ca,Sr,Ba)Nb₂O₆·*n*H₂O or (Ca,Sr,Ba)_{2-*x*}Nb₂O₆(OH)_{1-*y*}·*n*H₂O (*x* ~ 1, *y* ~ 1, *n* ~ 1.5). The maximum amount of H₂O which can be accommodated in the structure of pyrochlore, is given as 1 + 3/8*x* where *x* is cation deficiency at the *A*-site (Ercit *et al.*, 1994). For Ba-strontio-pyrochlore, this value (~1.4) is in a good agreement with the amount of H₂O estimated by difference of analysis totals to 100% (~1.5). This implies that cation deficiency at the *A*-site and

anion deficiency at the *Y*-site are compensated by molecular H₂O entering the structure.

At present, evolutionary trends of pyrochlore compositions in the carbonatite rock series are not completely understood. Pyrochlore close to the ideal composition NaCaNb₂O₆(F, OH) with low-to-moderate *LREE*, Sr, Ti and Th occurs in a broad variety of carbonatites and related metasomatic rocks ('second' and 'third' pyrochlore generations: Kapustin, 1980; 'ideal' pyrochlore: Mariano *et al.*, 1997; pyrochlore C: Petruk and Owens, 1975; Wall *et al.*, 1996). Th-rich (ThO₂ > 4 wt.%) pyrochlore is not characteristic of carbonatites and has been encountered only in a few localities (Vuorijarvi, Kola: Epshtein *et al.*, 1991; Guli, Siberia: Williams and Kogarko, 1996). Data available from the literature (Kapustin, 1980; Williams, 1996; Williams and Kogarko, 1996) suggest that pyrochlore ('hatchettolite') from early calcite carbonatites and phoscorites is enriched in Ta₂O₅ (up to 25.6 wt.%), TiO₂ (up to 11.4 wt.%) and UO₂ (up to 20.4 wt.%) relative to pyrochlore from late-stage carbonatites. This is in a good agreement with relatively low TiO₂ and not detectable Ta₂O₅ and UO₂ contents in pyrochlore from apatite-dolomite carbonatite of the Lesnaya Varaka complex.

Pyrochlores enriched in Sr, Ba, *LREE* and, less commonly, K are typical for weathered carbonatites and related rocks and, in most cases, form

TABLE 3. Representative compositions of barian strontio-pyrochlore

| | 1 | 2 | 3 | 4 | | 1 | 2 | 3 | 4 |
|--------------------------------|-------|-------|-------|-------|--|-------|-------|-------|-------|
| Wt. % | | | | | Structural formulae (ΣB -cations = 2) | | | | |
| Na ₂ O | 0.91 | 0.66 | 0.45 | 0.31 | Na | 0.117 | 0.084 | 0.061 | 0.043 |
| CaO | 6.27 | 5.54 | 4.50 | 3.89 | Ca | 0.445 | 0.392 | 0.336 | 0.297 |
| SrO | 6.28 | 7.90 | 8.24 | 8.91 | Sr | 0.241 | 0.303 | 0.333 | 0.369 |
| BaO | 3.38 | 3.18 | 5.16 | 6.28 | Ba | 0.088 | 0.082 | 0.141 | 0.176 |
| La ₂ O ₃ | n.d. | 0.69 | 0.33 | 0.97 | La | 0.000 | 0.017 | 0.008 | 0.026 |
| Ce ₂ O ₃ | 1.35 | 2.47 | 1.86 | 2.08 | Ce | 0.033 | 0.060 | 0.047 | 0.054 |
| Nd ₂ O ₃ | 0.25 | 0.23 | n.d. | 0.10 | Nd | 0.006 | 0.005 | 0.000 | 0.002 |
| ThO ₂ | 3.80 | 4.32 | 3.48 | 3.35 | Th | 0.057 | 0.065 | 0.056 | 0.054 |
| | | | | | ΣA | 0.987 | 1.008 | 0.982 | 0.971 |
| TiO ₂ | 4.40 | 4.60 | 3.41 | 4.08 | Ti | 0.219 | 0.228 | 0.178 | 0.219 |
| Fe ₂ O ₃ | 1.30 | 1.28 | 1.75 | 1.56 | Fe | 0.065 | 0.064 | 0.092 | 0.084 |
| Nb ₂ O ₅ | 57.26 | 57.17 | 54.91 | 52.60 | Nb | 1.716 | 1.708 | 1.730 | 1.697 |
| Total | 85.20 | 88.04 | 84.09 | 84.13 | | | | | |

Total Fe expressed as Fe₂O₃;

F was not detected on EDS spectra.

n.d. = not detected.

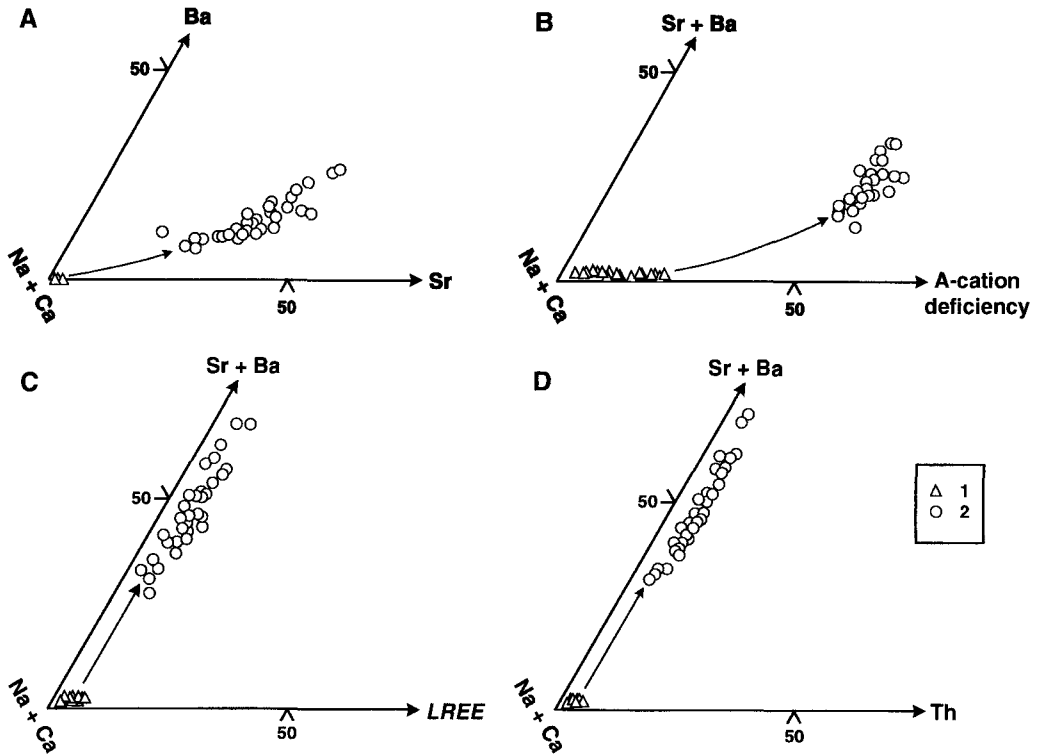


FIG. 4. Compositional variation of pyrochlore-group minerals from the Lesnaya Varaka carbonatite. 1 Na-Ca pyrochlore, 2 barian strontipyrochlore. For discussion see text.

due to secondary alteration of primary Na-Ca pyrochlore (Lapin and Kulikova, 1989; Lottermoser and England, 1988; Lumpkin and Ewing, 1995; Mariano *et al.*, 1997; Van Wambeke, 1978; Wall *et al.*, 1996). The secondary alteration involves cation and anion leaching, cation exchange and hydration of primary pyrochlore, but does not affect the actinide elements (Lumpkin and Ewing, 1995). Primary alteration of carbonatitic pyrochlore by late-stage hydrothermal fluids also involves loss of cations at the A-site and anions at the Y-site, as well as an increase in Sr content, but proceeds to a lesser extent in terms of anion and cation deficiency (Lumpkin and Ewing, 1995). Secondary strontipyrochlore compositionally similar to that described in this study, has been previously observed in a number of carbonatite localities including the Lueshe complex, Zaire (Wall *et al.*, 1996), Mt. Weld, Australia (Lottermoser and England, 1988) and some Siberian complexes (Lapin *et al.*, 1988; Lapin


and Kulikova, 1989). The only known occurrence of primary strontipyrochlore is Mt. Vavnbéd, Lovozero complex, Kola Peninsula. At this locality, strontipyrochlore (up to 84 % A-site occupied by Sr) occurs as inclusions in a hydrothermal albite-aegirine paragenesis (Voloshin *et al.*, 1989). This mineral differs from the secondary strontipyrochlore in showing regular zonation patterns with outer zones commonly enriched in Na and Ca, and depleted in Ba (Voloshin *et al.*, 1989).

Monazite-(Ce).

This mineral shows significant intergranular variation in composition. Individual grains may or may not exhibit irregular, 'patchy' zonation. Apart from the LREE, dominated by Ce, this mineral contains significant Ca, Sr and Th (Table 4). Previous studies (Bowie and Horne, 1953; Kukharencó *et al.*, 1965) demonstrate that these cations may be accommodated in monazite according to the following substitution schemes:

TABLE 4. Representative compositions of monazite-(Ce)

| | 1 | 2 | 3 | 4 | | 1 | 2 | 3 | 4 |
|--------------------------------|--------|--------|-------|-------|--|-------|-------|-------|-------|
| Wt. % | | | | | Structural formulae ($\Sigma O = 4$) | | | | |
| CaO | 0.92 | 1.55 | 4.00 | 2.81 | Ca | 0.039 | 0.067 | 0.171 | 0.122 |
| SrO | 5.17 | 6.03 | 7.54 | 8.33 | Sr | 0.119 | 0.141 | 0.174 | 0.197 |
| La ₂ O ₃ | 15.14 | 10.80 | 0.46 | 0.62 | La | 0.221 | 0.161 | 0.007 | 0.009 |
| Ce ₂ O ₃ | 29.18 | 25.08 | 22.33 | 14.78 | Ce | 0.423 | 0.370 | 0.326 | 0.220 |
| Pr ₂ O ₃ | 3.85 | 4.64 | 3.29 | 2.96 | Pr | 0.056 | 0.068 | 0.048 | 0.044 |
| Nd ₂ O ₃ | 8.77 | 9.02 | 5.16 | 5.50 | Nd | 0.124 | 0.130 | 0.073 | 0.080 |
| ThO ₂ | 9.74 | 14.96 | 26.53 | 34.94 | Th | 0.088 | 0.137 | 0.240 | 0.324 |
| P ₂ O ₅ | 29.00 | 28.38 | 29.58 | 29.06 | P | 0.972 | 0.969 | 0.998 | 1.001 |
| Total | 101.77 | 100.46 | 98.89 | 99.00 | | | | | |



All compositions obtained in this study are pure phosphates and, therefore, the latter two schemes have to be ruled out. The first substitution scheme represents a solid solution series between monazite-(Ce) CePO_4 , brabantite $\text{CaTh}(\text{PO}_4)_2$ and $\text{SrTh}(\text{PO}_4)_2$. Brabantite is a rare mineral, previously encountered only in granite pegmatites at Brabant, Namibia (Rose, 1980) and two localities in Travancore, India (Bowie and Horne, 1953). The samples from Travancore have significant monazite and huttonite (ThSiO_4) contents and have been classified by Bowie and Horne (1953) as 'cheralite', a mineral intermediate between CePO_4 and $\text{CaTh}(\text{PO}_4)_2$. Although the name 'cheralite' used by Bowie and Horne (1953) to describe this mineral has chronological priority, we favour the term 'brabantite' as most closely corresponding to the end-member composition $\text{CaTh}(\text{PO}_4)_2$ (Rose, 1980). Experimental studies by Podor and Cuney (1997) prove complete solubility between CePO_4 and $\text{CaTh}(\text{PO}_4)_2$ at geological conditions. $\text{SrTh}(\text{PO}_4)_2$ is not known as a distinct mineral species, but has been synthesized by solid-state reaction and shown to be monoclinic and isostructural with monazite (Rose, 1980).

The compositions of LREE-phosphate from Lesnaya Varaka plot mostly into the monazite-(Ce) part of the ternary system CePO_4 - $\text{CaTh}(\text{PO}_4)_2$ - $\text{SrTh}(\text{PO}_4)_2$, but show strong enrichment in $\text{SrTh}(\text{PO}_4)_2$ (Fig. 5). Only a few compositions represent a distinct mineral species with the general formula $\text{SrTh}(\text{PO}_4)_2$. The

variational trend demonstrates that the enrichment in $\text{SrTh}(\text{PO}_4)_2$ is combined with an increase in the brabantite component (Fig. 5). It is noteworthy that the most Th-enriched monazite compositions are systematically depleted in La (Table 4, anal. 3 and 4). This feature cannot be explained unequivocally due to the lack of structural data. We suggest that incorporation of Th results in the contraction of the monazite lattice, and makes the cation site unsuitable for the relatively large La^{3+} .

Although monazite is an ubiquitous accessory phase in carbonatites and sometimes form commercially viable deposits (Mariano, 1989), there is no modern systematic study of its composition. Scarce data available from the literature show that monazite from carbonatites is compositionally close to that of its ideal formula (Kapustin, 1980). At different carbonatite localities, the abundance of different LREE varies, but Ce is always dominant. The only other known occurrence of Ca-Th-rich (4.6 wt.% CaO and 5.8 wt.% ThO_2) monazite-(Ce) in carbonatite is the Vuorijarvi complex, Kola Peninsula (Kukhareno *et al.*, 1965). However, this mineral initially described as sulphate-monazite, differs from the Lesnaya Varaka samples in containing significant CaSO_4 and ThSiO_4 and being depleted in Sr (Kukhareno *et al.*, 1965).

Compositional data on secondary monazite found in the laterite crusts covering carbonatite deposits, are limited to a few microprobe analyses (Lottermoser, 1990). This mineral is poor in SrO and ThO_2 and sporadically-enriched in CaO (up to 4.7 wt.%; Lottermoser, 1990). However, the presence of hexagonal brockite $\text{CaTh}(\text{PO}_4)_2 \cdot n\text{H}_2\text{O}$ in some carbonatite laterites

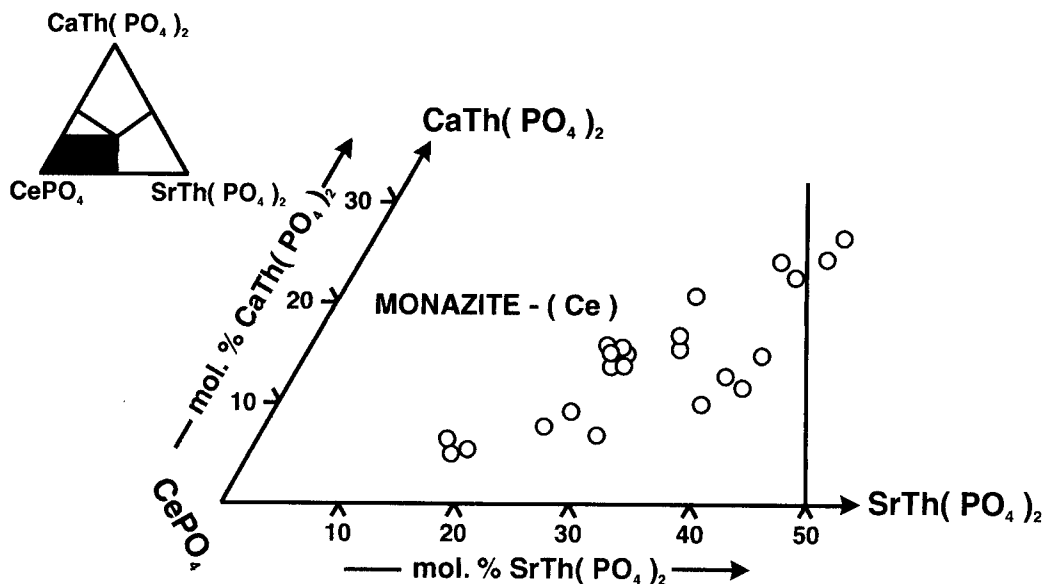


FIG. 5. Compositions (mol.%) of phosphates from the Lesnaya Varaka carbonatite in the ternary system monazite-(Ce) CePO_4 -brabantite $\text{CaTh}(\text{PO}_4)_2$ - $\text{SrTh}(\text{PO}_4)_2$.

(Mariano, 1989), suggests that Ca- and Th-enriched monazite-(Ce) or brabantite may also be found in this type of *LREE* deposits.

X-ray powder diffractometry

X-ray diffraction (XRD) powder patterns were obtained with a Philips 3710 diffractometer (Cu radiation) at Lakehead University, Ontario, using a Philips Debye-Scherrer type camera with a diameter of 114.6 mm. The diffractometer was operated at 40 kV and 20 mA. Relative intensities of the diffraction lines were estimated visually from the films.

The mineral developed as black cores of the intergrowths, gives an XRD pattern typical of perovskite-type compounds (Table 5). Splitting of the most intense diffraction line, the presence of several 'extra' lines on the pattern and optical properties of the mineral (see above), suggest that it is lueshite, the orthorhombic NaNbO_3 polymorph from the perovskite group (Safiannikoff, 1959), rather than cubic isolueshite (Chakhmouradian *et al.*, 1997).

The pyrochlore-group minerals which form the honey-yellow rim are metamict, but may be restored to crystallinity after heating to 800°C for 1 hour. Upon heating, Na-Ca pyrochlore restores a pyrochlore-type structure (Table 5), while Ba-strontiochlorite gives an XRD pattern similar

to that of aeschynite-group minerals (Table 6, vigezzite is given as an example). The XRD pattern of Ba-strontiochlorite also includes a few faint diffraction lines corresponding to the strongest peaks of pyrochlore ($d = 5.95, 1.84, 1.56$). The aeschynite group includes a series of complex oxides with the general formula AB_2X_6 ($A = \text{REE}, \text{Ca}, \text{Th}, \text{Na}$; $B = \text{Nb}, \text{Ta}, \text{Ti}, \text{Fe}$; $X = \text{O}, \text{OH}$). As noted above, Ba-strontiochlorite from Lesnaya Varaka approaches the formula $(\text{Ca}, \text{Sr}, \text{Ba})\text{Nb}_2\text{O}_6 \cdot n\text{H}_2\text{O}$. Compositionally similar niobate hydrates $\text{ANb}_2\text{O}_6 \cdot n\text{H}_2\text{O}$ ($A = \text{Ca}, \text{Sr}, \text{Ba}$) were synthesized from aqueous solutions by Krylov and Alekseev (1954; 1955). Upon heating, these polyhydrates first transform to monohydrates at 110–300°C, and then to anhydrous salts at 250–480°C (Krylov and Alekseev, 1954; 1955). It is important to note that the niobate hydrates of alkali-earth elements have a structure similar to that of CaF_2 (or pyrochlore) and accommodate the water molecules in the large 'cages' within the lattice (Krylov and Alekseev, 1955). Therefore, we may propose that upon heating, metamict Ba-strontiochlorite became dehydrated and recrystallised to an aeschynite-type structure. Apparently, the latter is the most stable structural state of anhydrous Sr-rich CaNb_2O_6 . The commonest naturally-occurring form of pure Ca niobate (CaNb_2O_6) is fersmite; its structure is orthorhombic (Table 6) and similar to that of columbite

TABLE 5. X-ray diffraction patterns of lueshite and Na-Ca pyrochlore

| <i>hkl</i> | 1 <i>d</i> | <i>I/I</i> ₀ | <i>hkl</i> | 2 <i>d</i> | <i>I/I</i> ₀ |
|--------------|---------------|-------------------------|------------|---------------|-------------------------|
| 101 | 3.91 | 80 | 111 | 5.95 | 30 |
| 200 | 2.88 | 20 | 311 | 3.13 | 20 |
| 141, 002 | 2.76 | 100 | 222 | 2.98 | 100 |
| 161 | 2.18 | <10 | 400 | 2.59 | 20 |
| 202 | 1.947 | 50 | 333, 511 | 1.99 | 10 |
| 023, 162 | 1.795 | 10 | 440 | 1.835 | 70 |
| 371, 282 | 1.382 | 40 | 622 | 1.564 | 50 |
| 381 | 1.303 | 30 | 444 | 1.502 | 10 |
| 343, 412 | 1.236 | 40 | 553, 731 | 1.353 | 10 |
| 442, 244 | 1.180 | 10 | 800 | 1.301 | 10 |
| | | | 662 | 1.196 | 20 |
| | | | 840 | 1.166 | 10 |
| | | | 844 | 1.062 | 10 |
| | | | 10.22, 666 | 1.001 | 10 |
| <i>a</i> , Å | 5.76(2) | | | 10.396(5) | |
| <i>b</i> , Å | 15.62(8) | | | | |
| <i>c</i> , Å | 5.30(2) | | | | |

1 lueshite, Lesnaya Varaka;

2 Na-Ca pyrochlore heated to 800°C for 1 h, Lesnaya Varaka.

(Aleksandrov, 1960; Cummings and Simonsen, 1970; Shabalín, 1981). The other mineral with the general formula CaNb_2O_6 is vigezzite. It is isostructural with aeschynite, occurs only at a few localities (Graeser *et al.*, 1979; Subbotin and Men'shikov, 1987), and is not known to exist in a synthetic form. As suggested by Graeser *et al.* (1979) the aeschynite structure of vigezzite may be stabilized by REE and Ti cations. The $(LREE)_2\text{O}_3$ content in Ba-strontio-pyrochlore examined in this study is low, but SrO is very high, suggesting that Sr may play a stabilizing role in the aeschynite-type lattice. Indeed, one of the SrNb_2O_6 polymorphs is isostructural with aeschynite and has either orthorhombic (Whiston and Smith, 1967) or monoclinic (Brusset *et al.*, 1971) symmetry (Table 6). Further discussion on structural relationships between pyrochlore and related Ca-Sr niobates is beyond the scope of this work.

Discussion

The genesis of carbonate-bearing rocks associated with the alkaline ultramafic complexes, is a subject of extensive petrological discussion. Recent studies demonstrate that the formation of carbonatites (*sensu lato*) at Kola Peninsula was a multi-stage process involving magmatic as well as

late-stage re-equilibration and metasomatic phenomena (Bulakh and Ivanikov, 1996; Subbotin and Mikhaelis, 1986; Zaitsev and Bell, 1995; Zaitsev and Polezhaeva, 1994). In the Kola intrusions, dolomite carbonatites are relatively rare, compared with the calcite-dominated varieties. Textural features suggest that some dolomite in the Kola carbonatites is exsolved from early magnesian calcite or is a product of late-stage dolomitization by Mg-rich fluids (Kapustin, 1984; Zaitsev and Polezhaeva, 1994). Kukharenko *et al.* (1965, pp. 733–4) note that, although some dolomite carbonatites occur in the form of intrusive bodies, the evidence for their magmatic origin is inadequate. These authors interpret the geological setting of Lesnaya Varaka carbonatite and its textural features (see above) to be a result of metasomatic replacement of the wall-rock ultramafites in a tectonically active environment. Kapustin (1984) also suggests a metasomatic origin for the Lesnaya Varaka carbonatite. However, as demonstrated by Harmer and Gittins (1997), intrusive dolomite carbonatites are fairly common in a number of alkaline provinces and primary magnesian carbonatite melts may be a source of calciocarbonatites, but not *vice versa*. Further isotopic and experimental studies are required to reveal the nature of

MINERALS IN APATITE-DOLOMITE CARBONATITE

 TABLE 6. X-ray diffraction patterns of heated barian strontiochlorite, vigezzite, SrNb₂O₆ and fersmite

| 1 | | | 2 | | 3 | | | 4 | | |
|--------------|--------------|------------------------|----------|--------------------------------|------------|----------|------------------------|------------|----------|------------------------|
| <i>hkl</i> | <i>d</i> | <i>I/I_o</i> | <i>d</i> | <i>I/I_o</i> | <i>hkl</i> | <i>d</i> | <i>I/I_o</i> | <i>hkl</i> | <i>d</i> | <i>I/I_o</i> |
| 011 | | | 4.821 | 90 | 101 | 4.99 | 8 | 020 | 7.47 | 40 |
| 021 | 3.86 | 10 | 3.854 | 10 | 201 | 3.93 | 6 | 110 | 5.34 | 20 |
| 200 | | | 3.784 | 80 | 020 | 3.86 | 20 | 130, 111 | 3.75 | 60 |
| 121 | 3.43 | 10 | | | | | | 121 | 3.428 | 20 |
| 220 | 3.13 | 20 | 3.117 | 10 | 220 | 3.158 | 16 | 131 | 3.049 | 100 |
| 031 | 3.04 | 60 | 3.036 | 100 | 301 | 3.065 | 100 | 200 | 2.863 | 30 |
| 211 | 2.98 | 100 | 2.974 | 100 | | | | 141, 220 | 2.681 | 10 |
| 131 | | | 2.802 | 20 | 311 | 2.852 | 5 | 002 | 2.606 | 20 |
| 040 | 2.76 | 10 | 2.763 | 30 | 002 | 2.803 | 20 | 012 | 2.564 | 10 |
| 002 | | | 2.684 | 40 | 221 | 2.752 | 6 | 201 | 2.510 | 30 |
| 231 | | | 2.367 | 40 | 031 | 2.336 | 6 | 060 | 2.489 | 30 |
| 240 | | | 2.229 | 30 | 420 | 2.239 | 6 | 151 | 2.368 | 5 |
| 202 | | | 2.187 | 5 | 122 | 2.223 | 5 | 032 | 2.306 | 10 |
| 212 | | | 2.145 | 20 | 222 | 2.095 | 12 | 231 | 2.242 | 20 |
| 042 | 1.925 | 10 | 1.9226 | 20 | 511 | 1.980 | 5 | 132, 042 | 2.139 | 10 |
| 400 | 1.876 | 10 | 1.8885 | 30 | 402 | 1.964 | 8 | 161, 241 | 2.090 | 20 |
| 341 | 1.755 | 20 | | | 322 | 1.928 | 18 | 142, 170 | 2.004 | 10 |
| 242 | | | 1.7128 | 60 | 103 | 1.840 | 6 | 052 | 1.962 | 20 |
| 431 | 1.595 | 10 | 1.6018 | 70 | 600 | 1.833 | 7 | 202, 251 | 1.927 | 30 |
| 261 | 1.590 | 10 | | | 422 | 1.749 | 12 | 212 | 1.916 | 5 |
| 252 | | | 1.5512 | 40 | 601 | 1.742 | 14 | 260 | 1.879 | 40 |
| 071 | 1.518 | 10 | 1.5112 | 30 | 123 | 1.661 | 16 | 062, 232 | 1.799 | 50 |
| 271 | | | 1.4028 | 40 | 341 | 1.633 | 6 | 330, 311 | 1.784 | 30 |
| | | | | | 313 | 1.627 | 11 | 261 | 1.768 | 50 |
| | | | | | 223 | 1.607 | 8 | 331, 181 | 1.688 | 20 |
| | | | | | 621 | 1.588 | 8 | 113, 072 | 1.653 | 10 |
| | | | | | 700 | 1.572 | 5 | 252, 123 | 1.622 | 30 |
| | | | | | 323 | 1.528 | 6 | 133 | 1.576 | 20 |
| | | | | | 242 | 1.526 | 8 | 351, 312 | 1.537 | 70 |
| | | | | | 033 | 1.511 | 12 | | | |
| System | orthorhombic | | | orthorhombic (? monoclinic) | | | orthorhombic | | | |
| Sp. gr. | <i>Pmnb</i> | | | n/a | | | <i>Pcan</i> | | | |
| <i>a</i> , Å | 7.53(2) | | | 7.56(1) | | | 5.73 | | | |
| <i>b</i> , Å | 11.16(3) | | | 11.03(1) | | | 14.94 | | | |
| <i>c</i> , Å | 5.20(4) | | | 5.360(4) | | | 5.22 | | | |

1 Ba-strontiochlorite heated to 800°C for 1 h, Lesnaya Varaka (this work);

2 vigezzite, Valle Vigezzo, Italy (Graeser *et al.*, 1979);

3 SrNb₂O₆ (ASTM 28-1243, diffraction lines with *I/I_o* < 5 are omitted);

4 fersmite (ASTM 18-302).

n/a = not available.

apatite-dolomite carbonatite at the Lesnaya Varaka pluton.

In this rock, lueshite is the earliest Nb mineral to crystallize after anatase, ilmenite and the majority of dolomite and fluorapatite. The latter four minerals are commonly found as inclusions in the crystals of lueshite. At late stages of carbonatite evolution, lueshite was partly replaced

and overgrown by Na-Ca pyrochlore. Experimental data (Jago and Gittins, 1993) indicate that, compared to pyrochlore, crystallization of lueshite is promoted by a lower F content and higher alkalinity of the carbonatite system. Therefore, the appearance of lueshite at the early stage of carbonatite evolution reflects a relatively high Na/Ca ratio in the residual melt/

fluid after the crystallization of dolomite and fluorapatite, and a depletion of the system in F due to precipitation of fluorapatite. Crystallization of lueshite and loss of Na during metasomatic alteration of the wall rocks brought about gradual decrease in the Na/Ca ratio of the system. This is documented by core-to-rim zonation pattern of lueshite crystals (see above) and appearance of richterite in the tremolite contact zones rimming the carbonatite dikes at Lesnaya Varaka (Kukhareenko *et al.*, 1965).

The replacement of Na-Ca pyrochlore by Ba-strontiochlorite involved hydration, cation exchange at the *A*-site and loss of ions at the *A*- and *Y*-sites. A general pattern and extent of alteration in terms of ionic deficiency and hydration, suggest that this was a low-temperature hydrothermal or perhaps, secondary process (Lumpkin and Ewing, 1995). In this process, fluorapatite and strontianite were a major source of Sr, while a primary Ba host is unknown. Compositionally similar strontiochlorite occurs in a number of weathered carbonatites including the Lueshe complex, Zaire (Lumpkin and Ewing, 1995; Wall *et al.*, 1996), Mt. Weld, Australia (Lottermoser and England, 1988), Enisei Ridge and other occurrences in Siberia (Lapin *et al.*, 1986; Lapin and Kulikova, 1989). Interestingly, secondary pyrochlore from Lesnaya Varaka does not exhibit enrichment in *LREE*, which suggests that most of *LREE* leached from fluorapatite and early Nb minerals was precipitated in the form of phosphates. These show an extensive compositional variation, and represent the ternary system monazite-(Ce) CePO_4 -brabantite $\text{CaTh}(\text{PO}_4)_2$ -SrTh $(\text{PO}_4)_2$. This demonstrates a high capacity of secondary monazite-(Ce) toward the actinide elements and accompanying divalent cations, that has a direct implication to the problem of conservation of radioactive wastes. In combination with the experimental data of Podor and Cuney (1997), those obtained in this study show that Th-doped monazite is stable in a broad range of geological conditions.

XRD study showed that, upon heating, Ba-strontiochlorite from the Lesnaya Varaka carbonatite produces the aeschynite-type structure. Based on these results, this mineral could be classified as strontian vigezzite, but this name would refer to the heated material rather than to the original phase containing significant molecular H_2O . The latter compositionally approaches synthetic compounds known to crystallize with the pyrochlore structure (Krylov and Alekseev,

1954; 1955). The majority of secondary Sr-, Ba-, *LREE*- and K-rich pyrochlores described in the literature, are strongly hydrated and exhibit high ionic deficiency. For example, kalipyrochlore from the Lueshe carbonatite (Zaire) has 92–98% cation deficiency at the *A*-site and contains more than 16 wt.% H_2O , thus compositionally approaching $\text{Nb}_2(\text{O},\text{OH})_6 \cdot 1.75\text{H}_2\text{O}$ (Ercit *et al.*, 1994; Wall *et al.*, 1996). However, even such defect phases as kalipyrochlore retain the pyrochlore structure which is stabilized by H_2O molecules entering partially or completely vacant *A*- and *Y*-sites (Ercit *et al.*, 1994). It is obvious that the secondary ion-deficient pyrochlores containing significant Sr, Ba or *LREE*, may undergo phase transitions during heating and loss of water.

Conclusions

The sample registered as 'natroniobite' in the archives of the Mineralogical Museum of St. Petersburg State University, Russia, is a complex aggregate of lueshite and its replacement products set in a matrix of dolomite and fluorapatite. The occurrence of lueshite, not pyrochlore, as a primary Nb mineral in this apatite-dolomite carbonatite suggests that a parental melt/fluid was enriched in Na and depleted in Ca and F after the crystallization of dolomite plus fluorapatite. The replacement of lueshite by Na-Ca pyrochlore documents evolution of the carbonatite system through the loss of Na. Barian strontiochlorite and monazite-(Ce), both showing extensive compositional ranges, are believed to form due to low-temperature hydrothermal or secondary (hypergene) alteration of the early mineral paragenesis including strontianite, fluorapatite, lueshite and Na-Ca pyrochlore.

Finally, we would like to point out that the object of the present paper is not to discredit natroniobite as we have not yet studied the holotype material. Further attempts will be made to obtain samples of this mineral from the type locality, as well as from the other occurrences (Sallanlatvi, Elet'ozero in Russia and Gem Park Complex in Colorado).

Acknowledgements

This study was supported by the Natural Sciences and Engineering Research Council of Canada and Lakehead University, Ontario (RHM, ARC). Frances Wall (The Natural History Museum,

London, U.K.) is thanked for a detailed constructive review of the early version of the manuscript. We are grateful to Prof. A.G. Bulakh (St. Petersburg State University, Russia) for useful discussion on the occurrence of natroniobite in the Kola carbonatites. Alan MacKenzie and Keith Pringnitz are thanked for their assistance with the analytical work, Ann Hammond and Sam Spivak for thin section preparation and drafting services, respectively.

References

- Aleksandrov, V.B. (1961) The crystal structure of fersmite. *Doklady AN SSSR, Earth Sci. Sect.*, **132**, 597–600.
- Bagdasarov, Yu. A., Gaidukova, V.S., Kuznetsova, N.N. and Sidorenko, G.A. (1962) A find of lueshite in Siberian carbonatites. *Doklady AN SSSR*, **147**, 1168–71 (in Russian).
- Bowie, S.H.U. and Horne, J.E.T. (1953) Cheralite, a new mineral of the monazite group. *Mineral. Mag.*, **30**, 93–9.
- Brusset, H., Gillier-Pandraud H. and Voliotis, S.D. (1971) Etude du polymorphisme du metaniobate de strontium SrNb_2O_6 (A study of polymorphism of strontium metaniobate SrNb_2O_6). *Mat. Res. Bull.*, **6**, 5–14.
- Bulakh, A.G. and Ivanikov, V.V. (1996) Carbonatites of the Turiy Peninsula, Kola: role of magmatism and of metasomatism. *Canad. Mineral.*, **34**, 403–9.
- Bulakh, A.G., Kukhareno, A.A., Knipovich, Yu.N., Kondrat'eva, V.V., Baklanova, K.A., Baranova, E.N. (1960) Some new minerals in carbonatites of the Kola Peninsula. *Mater. God. Sessii Uchenogo Sov. VSEGEI (Mat. Ann. Sci. Council Meeting)*, **1959**, 114–6 (in Russian). Abstracted in *Amer. Mineral.*, **47**, 1483.
- Chakmouradian, A.R., Yakovenchuk, V.N., Mitchell, R.H. and Bogdanova, A.N. (1997) Isolueshite, a new mineral of the perovskite group from the Khibina alkaline complex. *Eur. J. Mineral.*, **9**, 483–90.
- Cummings, J.P. and Simonsen, S.H. (1970) The crystal structure of calcium niobate (CaNb_2O_6). *Amer. Mineral.*, **55**, 90–7.
- Epshtein, E.M., Danil'chenko, N.A. and Nechelyustov, G.N. (1991) Hypogenic bariopyrochlore from a carbonatite complex. *Zap. Vses. Mineral. Obshch.*, **120**, 74–9 (in Russian).
- Ercit, T.S., Hawthorne, F.C. and Cerny, P. (1994) The structural chemistry of kalipyrochlore, a 'hydropyrochlore'. *Canad. Mineral.*, **32**, 415–20.
- Gorzhevskaya, S.A., Sidorenko, G.A. and Ginzburg, A.I. (1974) *Titano-tantalo-niobates*. Nedra Press, Moscow (in Russ.), 344 pp.
- Graeser, S., Schwander, H., Hanni, H. and Mattioli, V. (1979) Vigezzite, $(\text{Ca}, \text{Ce})(\text{Nb}, \text{Ta}, \text{Ti})_2\text{O}_6$, a new aeschynite-type mineral from the Alps. *Mineral. Mag.*, **43**, 459–62.
- Harmer, R.E. and Gittins, J. (1997) Dolomitic carbonatite parental magmas. *Ottawa '97 GAC/MAC Ann. Meeting, Prog. Abstr.*, A 64.
- Hogarth, D.D. (1989) Pyrochlore, apatite and amphibole: distinctive minerals in carbonatites. In *Carbonatites: Genesis and Evolution* (K. Bell, ed), Unwin Hyman, London, 105–48.
- Jago, B.C. and Gittins, J. (1993) Pyrochlore crystallization in carbonatites: the role of fluorine. *South African J. Geol.*, **96** (3), 149–59.
- Kapustin, Yu.L. (1980) *Mineralogy of Carbonatites*. Amerind Publishing Co, New Delhi, 259 pp.
- Kapustin, Yu.L. (1984) Carbonate relationships in metasomatically dolomitized carbonatite zones. *Doklady AN SSSR, Earth Sci. Sect.* **268**, 112–5.
- Kirilov, A.S. & Burova, T.A. (1967) Lueshites from carbonatites of the Kola Peninsula. In *Mineralogy and Geochemistry* (2). Leningrad Univ. Press, Leningrad, 28–39 (in Russian).
- Krylov, E.I. and Alekseev, Yu.I. (1954) Strontium metaniobate and its hydrates. *J. Gen. Chem. USSR*, **24**, 1883–6.
- Krylov, E.I. and Alekseev, Yu.I. (1955) Calcium and barium metaniobates and their hydrates. *J. Gen. Chem. USSR*, **25**, 1013–6.
- Kukhareno, A.A., Orlova, M.P., Bulakh, A.G., Bagdasarov, E.A., Rimskaya-Korsakova, O.M., Nefedov, E.I., Il'inskii, G.A., Sergeev, A.S. and Abakumova, N.B. (1965) *The Caledonian complex of ultrabasic alkaline rocks and carbonatites of the Kola Peninsula and Northern Karelia*. Nedra Press, Leningrad (in Russian), 772 pp.
- Kukhareno, A.A., Orlova, M.P. and Bagdasarov, E.A. (1969) *Alkaline gabbroids of Karelia*. Leningrad University Press, Leningrad (in Russ.), 184 pp.
- Lapin, A.V. and Kulikova, I.M. (1989) Processes of pyrochlore alteration and their products in the carbonatite weathering crusts. *Zap. Vses. Mineral. Obshch.*, **118**, 41–9 (in Russian).
- Lapin, A.V., Malyshev, A.A., Ploshko, V.V. and Cherepivskaya, G.Ye. (1988) Strontio-pyrochlore from lateritic weathered mantle of carbonatite. *Doklady AN SSSR, Earth Sci. Sect.*, **290**, 188–92.
- Lottermoser, B.G. (1990) Rare-earth element mineralisation within the Mt. Weld carbonatite laterite, Western Australia. *Lithos*, **24**, 151–67.
- Lottermoser, B.G. and England, B.M. (1988) Compositional variation in pyrochlores from the Mt. Weld carbonatite laterite, Western Australia. *Mineral. Petrol.*, **38**, 37–51.
- Lumpkin, G.R. and Ewing, R.C. (1995) Geochemical alteration of pyrochlore group minerals: Pyrochlore

- subgroup. *Amer. Mineral.*, **80**, 732–43.
- Mariano, A.N. (1989) Nature of economic mineralization in carbonatites and related rocks. In *Carbonatites: Genesis and Evolution* (K. Bell, ed.). Unwin Hyman, London, 149–76.
- Mariano, A.N., Lumpkin, G.R. and Leung, S.H.F. (1997) Ideal and defect pyrochlores from the Araxa carbonatite complex and laterite, Alto Paranaiba Province, Brasil. *Ottawa '97 GAC/MAC Ann. Meeting, Prog. Abstr.*, A 97.
- Mitchell, R.H. (1996) Perovskites: a revised classification scheme for an important rare earth element host in alkaline rocks. In: *Rare Earth Minerals: Chemistry, Origin and Ore Deposits* (A.P. Jones, F. Wall and C.T. Williams, eds), Chapman & Hall, London, 41–76.
- Mitchell, R.H. and Vladykin, N.V. (1993) Rare earth element-bearing tausonite and potassium barium titanates from the Little Murun potassic alkaline complex, Yakutia, Russia. *Mineral. Mag.*, **57**, 651–64.
- Orlova, M.P., Rozhdestvenskiy, Yu.P. and Baranova, E.N. (1963) On the mineralogy of rare-metal carbonatites of the Sallanlatvi massif (northern Karelia). *Trudy VSEGEI, New Ser.*, **96**, 3–20 (in Russian).
- Parker, R.L. and Sharp, W.N. (1970) Mafic-ultramafic igneous rocks and associated carbonatites of the Gem Park Complex, Custer and Fremont Counties, Colorado. *US Geol. Surv. Prof. Paper*, **649**, 24 p.
- Petruk, W. and Owens, D.R. (1975) Electron microprobe analyses for pyrochlore from Oka, Quebec. *Canad. Mineral.*, **13**, 282–5.
- Podor, R. and Cuney, M. (1997) Experimental study of Th-bearing LaPO_4 (780°C, 200 Mpa): Implications for monazite and actinide orthophosphate stability. *Amer. Mineral.*, **82**, 765–71.
- Rimskaya-Korsakova, O.M., Burova, T.A. and Frank-Kamenetskiy, V.A. (1963) Lueshite from carbonatites of the Kovdor massif. *Zap. Vses. Mineral. Obshchest.*, **92**, 173–83 (in Russian).
- Rose, D. (1980) Brabantite, $\text{CaTh}[\text{PO}_4]_2$, a new mineral of the monazite group. *Neues Jahrb. Mineral. Mh.*, 247–57.
- Safiannikoff, A. (1959) Un nouveau mineral de niobium (A new mineral of niobium). *Acad. Roy. Sciences d'Outre-Mer, Bull. Seances*, **5**, 1251–5.
- Shabalin, B.G. (1981) Synthesis conditions of rynerstonite, fersmite and their isostructural equivalents. *Mineral. Zhurnal*, **3**, 86–9 (in Russian).
- Subbotin, V.V. and Men'shikov, Yu.P. (1987) Accessory lueshite and viggezite from Sebljavr carbonatites. In *Mineral Assemblages and Minerals of Magmatic Complexes of the Kola Peninsula*. Kola Sci. Centre Press, Apatity, Russia, 69–76 (in Russian).
- Subbotin, V.V. and Mikhaelis, S.A. (1986) Genetic types of apatite ores of the Sebljavr complex deposit. In *Deposits of Non-metallic Resources in the Kola Peninsula*. Kola Sci. Centre Press, Apatity, Russia, 27–35 (in Russian).
- Van Wambeke, L. (1978) Kalipyrochlore, a new mineral of the pyrochlore group. *Amer. Mineral.*, **63**, 528–30.
- Voloshin, A.V., Pakhomovskii, Ya.A., Pushcharovskii, D.Yu., Nadezhina, T.N., Bakhchisaraitsev, A.Yu. and Kobiashev, Yu.S. (1989) Strontian pyrochlore: Composition and structure. *New data on minerals (Trudy Mineral. Muz. AN SSSR)*, **36**, 12–24 (in Russian).
- Wall, F., Williams, C.T. and Woolley, A.R. (1996) Pyrochlore from weathered carbonatite at Lueshe, Zaire. *Mineral. Mag.*, **60**, 731–50.
- Williams, C.T. (1996) The occurrence of niobian zirconolite, pyrochlore and baddeleyite in the Kovdor carbonatite complex, Kola Peninsula, Russia. *Mineral. Mag.*, **60**, 639–46.
- Williams, C.T. and Kogarko, L.N. (1996) New data on rare-metal mineralization in the Guli massif carbonatites, Arctic Siberia. *Geokhimiya*, **1996(6)**, 483–91 (in Russian).
- Whiston, C.D. and Smith, A.J. (1967) Double oxides containing niobium or tantalum. II. Systems involving strontium or barium. *Acta Crystal.*, **23**, 82–4.
- Zaitsev, A. and Bell, K. (1995) Sr and Nd isotope data of apatite, calcite and dolomite as indicators of source, and the relationships of phosphates and carbonatites. *Contrib. Mineral. Petrol.*, **121**, 324–35.
- Zaitsev, A. and Polezhaeva, L. (1994) Dolomite-calcite textures in early carbonatites of the Kovdor ore deposit, Kola peninsula, Russia: their genesis and application for calcite-dolomite geothermometry. *Contrib. Mineral. Petrol.*, **115**, 339–44.

[Manuscript received 27 October 1997:
revised 10 March 1998]